

Article

Nitrogen-Doped Cu₂O Thin Films for Photovoltaic Applications

Ørnulf Nordseth ^{1,*}, Raj Kumar ² , Kristin Bergum ², Irinela Chilibon ³, Sean Erik Foss ¹ and Edouard Monakhov ²

¹ Institute for Energy Technology (IFE), P.O. Box 40, NO-2027 Kjeller, Norway; Sean.Foss@ife.no

² Department of Physics/Center for Materials Science and Nanotechnology (SMN), University of Oslo, P.O. Box 1048, Blindern, NO-0316 Oslo, Norway; raj.kumar@smn.uio.no (R.K.); kristin.bergum@smn.uio.no (K.B.); edouard.monakhov@fys.uio.no (E.M.)

³ National Institute of Research and Development for Optoelectronics (INOE-2000), Bucharest-Magurele, Str. Atomistilor 409, RO-077125 Măgurele, Romania; chilib@inoe.ro

* Correspondence: ornulf.nordseth@ife.no; Tel.: +47-6380-6000

Received: 27 August 2019; Accepted: 17 September 2019; Published: 19 September 2019



Abstract: Cuprous oxide (Cu₂O) is a p-type semiconductor with high optical absorption and a direct bandgap of about 2.1 eV, making it an attractive material for photovoltaic applications. For a high-performance photovoltaic device, the formation of low-resistivity contacts on Cu₂O thin films is a prerequisite, which can be achieved by, for instance, nitrogen doping of Cu₂O in order to increase the carrier concentration. In this work, nitrogen-doped p-type Cu₂O thin films were prepared on quartz substrates by magnetron sputter deposition. By adding N₂ gas during the deposition process, a nitrogen concentration of up to 2.3×10^{21} atoms/cm³ in the Cu₂O thin films was achieved, as determined from secondary ion mass spectroscopy measurements. The effect of nitrogen doping on the structural, optical, and electrical properties of the Cu₂O thin films was investigated. X-ray diffraction measurements suggest a preservation of the Cu₂O phase for the nitrogen doped thin films, whereas spectrophotometric measurements show that the optical properties were not significantly altered by incorporation of nitrogen into the Cu₂O matrix. A significant conductivity enhancement was achieved for the nitrogen-doped Cu₂O thin films, based on Hall effect measurements, i.e., the hole concentration was increased from 4×10^{15} to 3×10^{19} cm⁻³ and the resistivity was reduced from 190 to 1.9 Ω·cm by adding nitrogen to the Cu₂O thin films.

Keywords: cuprous oxide; doping; nitrogen; thin film; magnetron sputtering

1. Introduction

Cuprous oxide (Cu₂O) is considered an attractive material for photovoltaic applications since it is a p-type semiconductor with high optical absorption and a direct bandgap of about 2.1 eV, yielding a theoretical power conversion efficiency limit close to 20% under 1 sun illumination [1]. To construct a p-n heterojunction, Cu₂O can be combined with various n-type metal oxide materials, such as for example ZnO, and accordingly, one can foresee a heterojunction solar cell fully based on low-cost, abundant, and non-toxic metal oxides [2]. The highest power conversion efficiency achieved experimentally for a n-ZnO/p-Cu₂O heterojunction solar cell is currently 8.1% [3], suggesting that further development of Cu₂O-based solar cells is required in order to realize their full potential [4]. A possible application of Cu₂O-based solar cells could be to combine them with conventional crystalline silicon (c-Si) solar cells in a mechanical stack of independently connected cells, enabling low-energy photons to be transmitted through the Cu₂O-based top subcell for subsequent absorption in the c-Si bottom subcell [5]. Such four-terminal tandem cell configuration has the potential to reach a power

conversion efficiency of above 30% under 1 sun illumination [6]. One possible way to enhance the performance of the ZnO/Cu₂O heterojunction solar cell could be to introduce a highly doped p-type layer at the back side of the Cu₂O absorber layer to reduce the charge carrier recombination at the rear surface and to form a low contact-resistance interface with low optical absorption [7,8], i.e., introduce a carrier (hole) selective passivating contact layer [9]. A highly doped layer can, for instance, be obtained by tuning of the electrical properties of Cu₂O by adding foreign atoms, such as nitrogen which is an abundant and non-toxic element that can be straightforwardly incorporated into the Cu₂O lattice [10]. Ideally, the doping should modify the electrical properties of Cu₂O without considerably affecting the physical and chemical properties. Previous investigations have suggested that nitrogen is a very effective p-type dopant when mixed into Cu₂O [11], acting as a substitutional impurity for oxygen atoms [10]. This dopant introduction should not result in formation of the deleterious CuO phase, which is detrimental for the electrical properties of the thin film. Moreover, a previous study on the effects of nitrogen doping on the optical properties of Cu₂O thin films indicated that the optical band gap could be affected by the incorporation of nitrogen [12].

The objective of this work was to investigate the effect of nitrogen doping on the electrical, structural, and optical properties of p-type Cu₂O thin films synthesized by direct current (DC) magnetron sputter deposition. The amount of nitrogen incorporated into the deposited Cu₂O thin films for various amount of N₂ gas in the process gas mix was analyzed by secondary ion mass spectroscopy (SIMS). Moreover, the crystallographic, morphological, optical, and electrical properties for nitrogen-doped Cu₂O thin films were determined from X-ray diffraction (XRD), atomic force microscopy (AFM), spectrophotometric, and Hall effect measurements, respectively. We showed that the electrical conductivity can be significantly enhanced by doping the Cu₂O thin films with nitrogen. For instance, the concentration of holes can be increased by more than three orders of magnitude by adding nitrogen into the Cu₂O thin films. Also, we showed that the incorporation of nitrogen into the Cu₂O thin films did not significantly affect surface morphology or the optical properties, and that the nitrogen-doped Cu₂O thin films remained phase pure.

2. Materials and Methods

Cu₂O thin films were deposited on quartz substrates by reactive sputtering of a Cu target (99.999%) using a DC magnetron sputtering system (Semicore Triaxis, Livermore, CA, USA). 1 × 1 cm² quartz substrates were cleaned in piranha solution (H₂SO₄ + H₂O₂) and rinsed in deionized water, blown dry with nitrogen, and loaded into the deposition chamber. The base pressure of the chamber was ~7 × 10⁻⁷ mbar. Prior to deposition, the Cu target was pre-sputtered for 15 min. During deposition, the substrate temperature was kept at 400 °C and the sample stage was rotated at a constant speed of 12 rotations per minute. The deposition power was fixed at 100 W. The nitrogen-doped Cu₂O (N:Cu₂O) thin film samples were prepared by varying the flow of process gases as shown in Table 1. The total gas flow was fixed at 50 standard cubic centimeters per minute (sccm) with variation in the Ar/N₂ flow ratio, whereas the O₂ flow was fixed at 7.5 sccm for all samples. The deposition time was constant for all samples.

Table 1. N:Cu₂O thin film sample naming and corresponding gas flows used during the sputter deposition process.

Sample Name	N ₂ /Ar/O ₂ (sccm)
Reference sample	0/42.5/7.5
1	1/41.5/7.5
2	2/40.5/7.5
3	3/39.5/7.5
4	5/37.5/7.5
5	10/32.5/7.5
6	15/27.5/7.5

SIMS measurements were carried out to analyze the nitrogen content of the N:Cu₂O thin films. The nitrogen concentration versus thin film depth was measured using a Cameca IMS 7f micro-analyzer (Gennevilliers, France) with primary beams of 15 keV Cs⁺ ions. ¹⁴N¹⁶O molecular ions were detected to quantify the nitrogen content in the thin films. The intensity-concentration calibration was performed using implanted Cu₂O as a reference sample. Depth conversion of the recorded profiles was performed by measuring the sputtered crater depth using a Dektak 8 stylus profilometer (Bruker, Billerica, MA, USA) and assuming a constant erosion rate. XRD patterns were recorded by a Bruker AXS D8 Discover (Billerica, MA, USA), using Cu K α -radiation and a Bragg–Brentano configuration. The thin film sample surface was analyzed using a Veeco Innova atomic force microscope (Bruker, Billerica, MA, USA), with a RTESPA Si doped probe. The scanning was carried out in tapping mode and the scanning speed was about 2.5 μ m/s. The AFM images had a resolution of 512 \times 512 pixels, and SPM Lab Analysis v.7.0 software (Lisboa, Portugal) was used for the image analysis. The UV–vis optical transmittance spectra in the wavelength range from 400 nm to 1500 nm were measured using a Shimadzu SolidSpe-3700 DUV spectrophotometer (Kyoto, Japan), a tungsten light source, and an integrating sphere. Room temperature Hall Effect measurements were carried out to determine the hole mobility, resistivity, and hole carrier density, using a LakeShore 7604 (Westerville, OH, USA) set up with the van der Pauw configuration.

3. Results and Discussion

3.1. Secondary Ion Mass Spectrometry Analysis

SIMS depth profiles for the N:Cu₂O thin film samples are shown in Figure 1a. The measured profiles indicate an increasing nitrogen concentration with increasing N₂ gas flow rate for the N:Cu₂O thin film samples. For the Cu₂O reference sample, a nitrogen concentration around 1×10^{18} atoms/cm³ was measured in the bulk of the thin film. However, near the interface to the quartz substrate the nitrogen concentration increased to $\sim 7 \times 10^{19}$ atoms/cm³ for the Cu₂O reference sample. This could possibly be a matrix effect due to deviation of the stoichiometry near the interface, or it could be related to ion mass interference, e.g., ¹⁴N¹⁶O molecular ions can be interfering with ³⁰Si, ²⁹SiH, or ²⁸SiH₂ ions. Based on the SIMS depth profiles shown in Figure 1a, the nitrogen concentration at a depth of 200 nm as well as the film thickness for the N:Cu₂O thin films are plotted in Figure 1b versus the N₂ gas flow. The data suggests that the nitrogen concentration in the N:Cu₂O thin films increases with increasing N₂ gas flow during the deposition process. For example, by increasing the N₂ gas flow from 1 to 15 sccm, the nitrogen concentration in the N:Cu₂O thin film is increased from 5.2×10^{20} to 2.3×10^{21} atoms/cm³. Moreover, the film thickness decreases with increasing N₂ gas flow rate, suggesting that the deposition rate for the N:Cu₂O thin film decreases with increasing N₂/Ar gas flow ratio during the sputter deposition process.

3.2. Structure and Morphology

Figure 2a shows XRD (θ – 2θ) scans for the N:Cu₂O thin film samples in the range 30°–75°, whereas the corresponding zoom-in for the range 35°–45° is shown in Figure 2b. The XRD data suggest that the N:Cu₂O thin films have a polycrystalline structure with diffraction peaks at $\sim 36.6^\circ$ and $\sim 42.6^\circ$, corresponding to reflection from the Cu₂O(111) and Cu₂O(200) planes, respectively. The phase of Cu₂O was determined by comparing the experimental XRD pattern with the Standard Powder Diffraction Cards (ICDD) patterns: 01-071-3645 or space group O_h^4 ; Pn3m, No. 224 for Cu₂O [13]. The θ – 2θ scans suggest that there is no obvious structural variation induced by the nitrogen doping and that the films remain phase pure with no presence of other Cu_xO phases, e.g., there are no diffraction peaks of the cupric oxide (CuO) and copper (III) oxide (Cu₄O₃) phases. Also, there are no diffraction peaks related to the Cu_xN phase observed for the N:Cu₂O thin film samples in the investigated 2θ range between 30° and 75° [14]. Figure 2b shows that the Cu₂O(111) and Cu₂O(200) diffraction peaks have shifted towards lower angles, e.g., for Sample 6, the peaks shifted by $\sim 0.4^\circ$ relative to those for the reference

sample, indicating that a small strain has been induced by the nitrogen doping. Furthermore, the $\text{Cu}_2\text{O}(200)$ diffraction peak is less dominant with respect to the $\text{Cu}_2\text{O}(111)$ diffraction peak for Sample 6 compared to that for the $\text{N}:\text{Cu}_2\text{O}$ thin film samples with less nitrogen concentration.

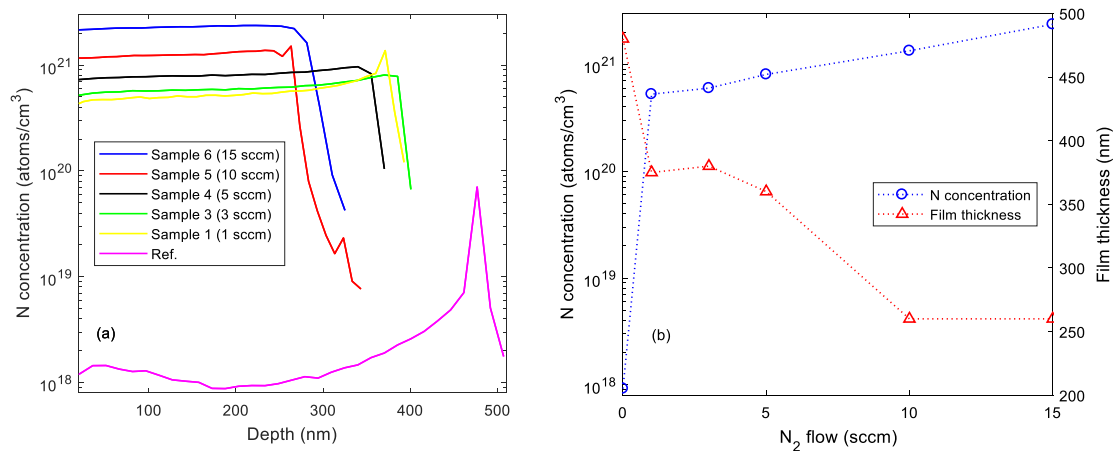


Figure 1. (a) Recorded SIMS depth profiles for $\text{N}:\text{Cu}_2\text{O}$ thin films deposited on quartz. (b) Nitrogen concentration and film thickness versus N_2 gas flow rate.

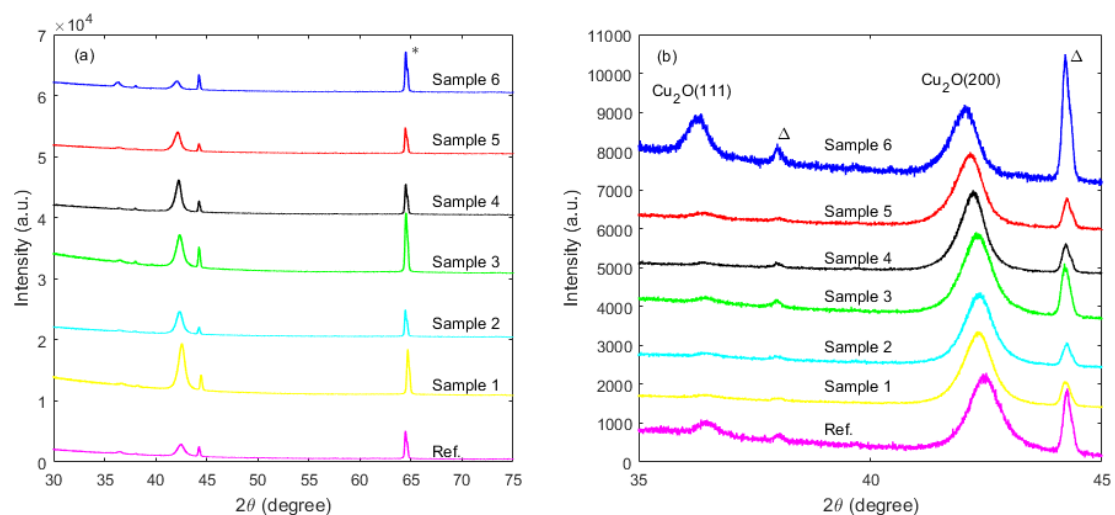


Figure 2. 2θ - θ scans for $\text{N}:\text{Cu}_2\text{O}$ thin films on quartz in the range (a) 30° – 75° and (b) 35° – 45° . The asterisk * indicates the peak of the quartz substrate, whereas Δ indicates the peaks of the sample holder.

Figure 3 shows AFM images of three different $\text{N}:\text{Cu}_2\text{O}$ thin film samples (for 5, 10 and 15 sccm N_2 gas flow rates), along with the Cu_2O reference sample. The AFM images suggest that there is no significant change in the surface morphology of the sputter deposited thin films when the N_2 gas flow rate is increased from 0 to 15 sccm, i.e., the grain size and texture is approximately the same for all four AFM images. The root-mean square surface roughness (R_{RMS}) for each thin film sample was extracted from the recorded AFM images. R_{RMS} is defined as the standard deviation of the surface height profile from the mean height, given by:

$$R_{RMS} = \left[\frac{1}{N} \sum_{i=1}^n (h_i - \langle h \rangle)^2 \right]^{\frac{1}{2}} \quad (1)$$

where N is the number of data points in the image, h_i is the height of the i th pixel, and h is the mean height of the image [15]. In Table 2, the R_{RMS} is given for each sample analyzed with AFM. The data

suggests that R_{RMS} varies between approximately 3 to 5 nm for all samples, and thus, the increase in N_2 gas flow rate up to 15 sccm has no major impact on the surface roughness of the N:Cu₂O thin films.

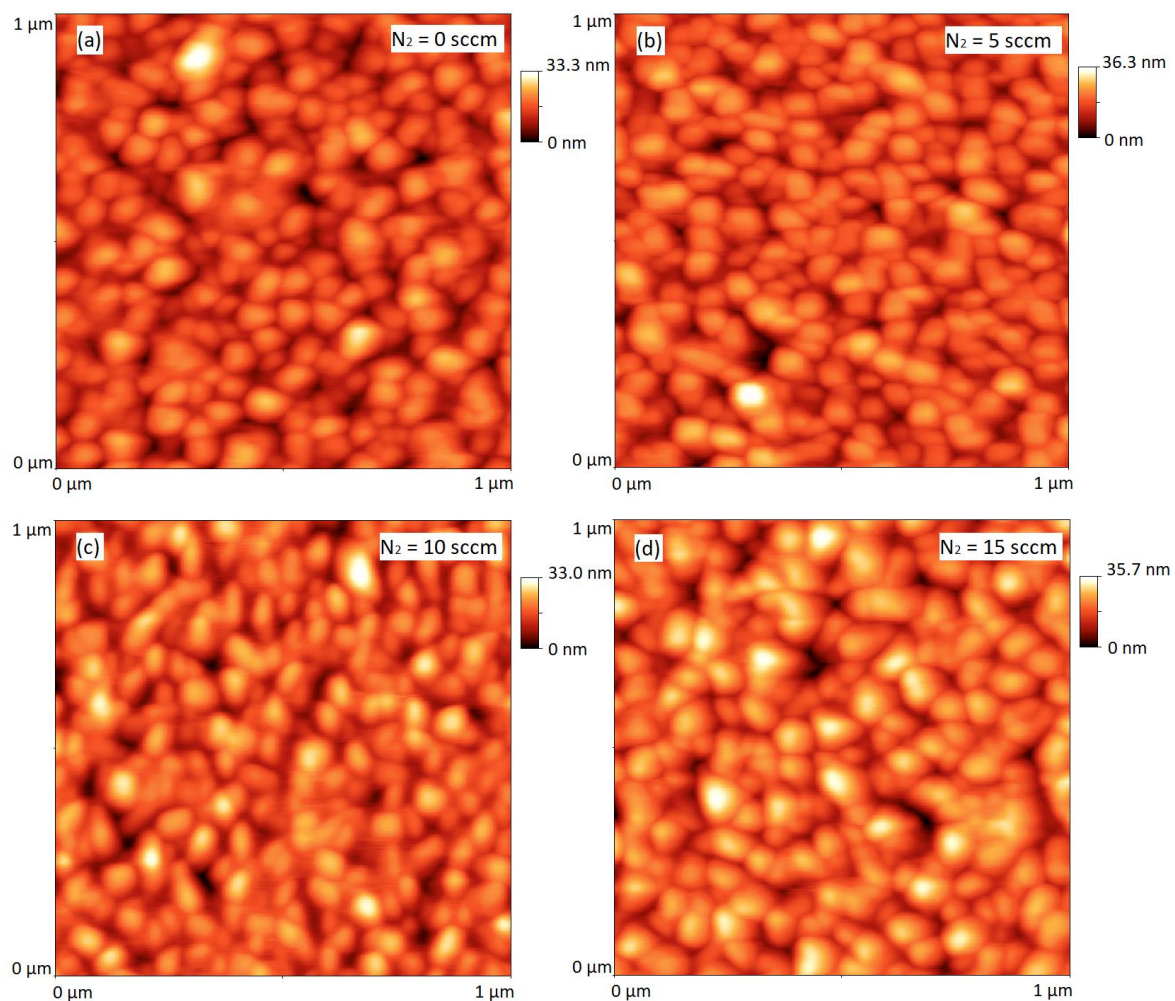


Figure 3. AFM images (1 $\mu\text{m} \times 1 \mu\text{m}$ size) for (a) the reference sample, (b) Sample 4, (c) Sample 5 and (d) Sample 6.

Table 2. N:Cu₂O thin film samples and corresponding root-mean square surface roughness (R_{RMS}) extracted from recorded AFM images.

Sample Name	N_2 Flow (sccm)	R_{RMS} (nm)
Reference sample	0	4.40
1	1	3.90
2	2	4.51
3	3	3.13
4	5	4.63
5	10	4.86
6	15	5.45

3.3. Optical Properties

The optical transmittance spectra in the wavelength range from 400 to 1500 nm for the N:Cu₂O thin film samples as well as for the Cu₂O reference sample are shown in Figure 4a. The data suggest that the thin films exhibit a transmittance of around 70% from the visible to the infrared wavelength range, whereas the high energy photons ($\lambda < 550$ nm) are absorbed. Thus, when applied, for instance, as a highly doped p-type N:Cu₂O layer at the back side of the Cu₂O absorber layer in a Cu₂O/c-Si

heterojunction tandem cell, the transmission of low-energy photons through the ZnO/Cu₂O top subcell will not be substantially affected. The optical absorption edges for the N:Cu₂O thin film samples were estimated by performing a Tauc plot analysis based on the optical transmittance spectra [16]. The resulting $(\alpha \cdot hv)^{1/n}$ versus (hv) curves (Tauc plots) for the N:Cu₂O thin films as well as for the Cu₂O reference sample are shown in Figure 4b, where α is the optical absorption coefficient and hv is the energy of the incident photons. For $n = 1/2$, the data show a linear relationship, which indicates a direct allowed optical transition in the N:Cu₂O thin films as well as for the Cu₂O reference sample [12]. By extrapolating the hv axis intercept of the line fitted on the linear portion of the Tauc plots, indicated by the dashed line in Figure 4b, the optical band gap energy (E_g) can be estimated. The Tauc plots suggest that the optical band gap energy is approximately 2.53 ± 0.02 eV for all the analysed films, which is consistent with the values for the optical band gap energy of N:Cu₂O films reported in the literature [14]. We observe that there is no apparent band-edge shift induced by the nitrogen doping of the Cu₂O films, which is consistent with the data reported by Ishizuka et al. [10]. However, Nakano et al. observed a possible optical band gap widening for N:Cu₂O thin films (E_g enlarged from 2.1 to 2.5 eV), as a result of a structural change induced by the nitrogen doping [12]. The XRD patterns shown in Figure 2b suggest that the nitrogen doping induces no significant structural change, which could be the reason why a band-edge shift is not observed for the sputter deposited Cu₂O thin films analyzed in this work.

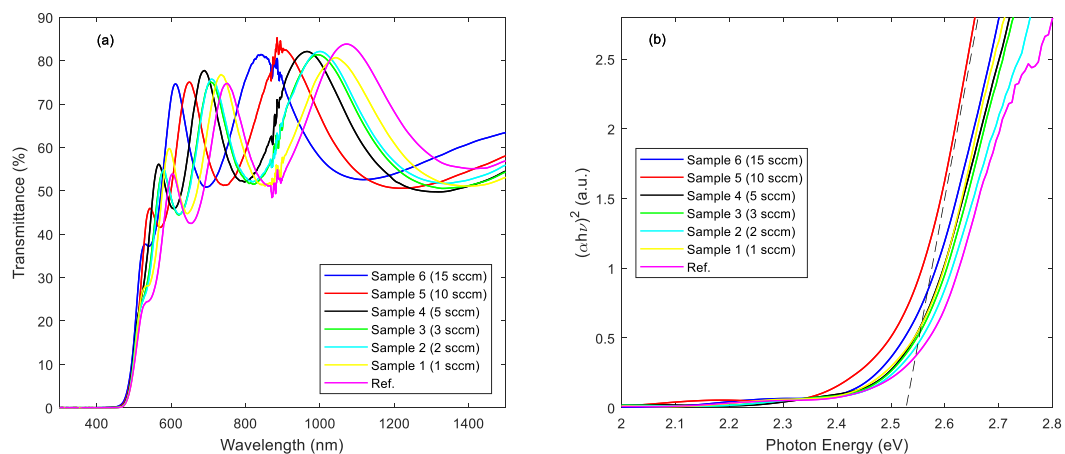


Figure 4. (a) Optical transmittance spectra and (b) corresponding Tauc plots for N:Cu₂O thin films and Cu₂O reference sample on quartz. The optical band gap energy for each sample was estimated from extrapolation to the abscissa (indicated by the dashed line).

3.4. Electrical Properties

The film resistivity, majority carrier (hole) density, and majority carrier (hole) mobility as a function of N₂ gas flow rate for the N:Cu₂O thin films on quartz are presented in Figure 5a–c, respectively. A p-type conductivity is observed for all samples analyzed in this work. Figure 5a shows that the film resistivity decreases with increasing N₂ gas flow rate. A resistivity of 1.9 Ω·cm was obtained for a N₂ gas flow rate of 15 sccm, which is 100 times lower than the resistivity of the Cu₂O reference sample. The film resistivity corresponds well with the film resistivity reported by Malerba et al. for Cu₂O films doped with up to 2.5% nitrogen [17]. Furthermore, the hole density increases with the N₂ gas flow rate, shown in Figure 5b. A hole density of around 3×10^{19} cm⁻³ is obtained for a N₂ gas flow rate of 10 sccm (Sample 5) and 15 sccm (Sample 6), which is more than three order of magnitudes higher than the hole density measured for the undoped Cu₂O reference sample. These results indicate that nitrogen doping is very effective in controlling the electrical properties of sputter deposited Cu₂O thin films. Figure 5c shows that the hole mobility decreases with increasing N₂ gas flow rate. The hole mobility is reduced from 13 cm²/V·s for the undoped Cu₂O reference sample to 0.1 cm²/V·s for Sample 6, processed with a N₂ gas flow rate of 15 sccm. The electrical characteristics for these films are in

agreement with those reported earlier for sputter-deposited polycrystalline N:Cu₂O thin films on glass [10,11]. The reduction of the carrier mobility with increasing N content can be ascribed to the presence of nitrogen atoms, acting as impurity scattering centers for free holes [11]. This suggests that the N atoms are in substitutional positions, which forms free holes by introducing shallow acceptor states in the band gap [10].

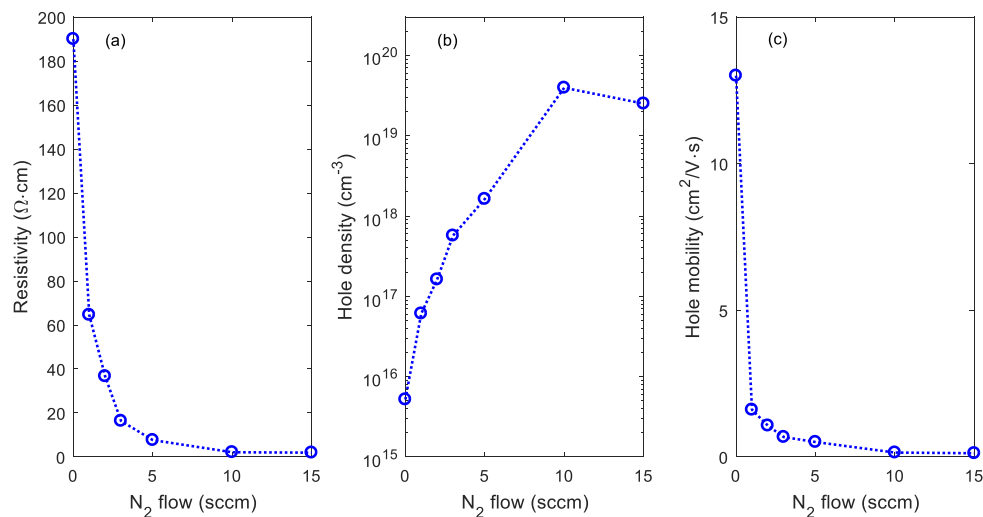


Figure 5. (a) Film resistivity, (b) majority carrier (hole) density, and (c) majority carrier (hole) mobility versus N₂ gas flow rate for N:Cu₂O thin films on quartz.

4. Conclusions

In summary, nitrogen-doped Cu₂O thin films were synthesized by reactive DC magnetron sputtering. Thin film samples were prepared by varying the Ar/N₂ gas flow ratio, while keeping the O₂ and the total gas flow rate fixed. SIMS depth profile analysis suggests that the nitrogen concentration in the N:Cu₂O thin films increases with increasing N₂ gas flow rate during the sputter deposition process. For example, by increasing the N₂ gas flow rate from 1 to 15 sccm, the nitrogen concentration in the N:Cu₂O thin film increases from 5.2×10^{20} to 2.3×10^{21} atoms/cm³. XRD characterization suggests that the N:Cu₂O films have a polycrystalline structure with a preferred (111) and (200) orientation. There is no obvious structural change induced by the nitrogen doping and the films remain phase pure with no presence of other Cu_xO or Cu_xN phases, which can be detrimental for the application of these films in heterojunction devices. The surface morphology of the sputter deposited Cu₂O thin films is not significantly affected by the nitrogen doping, as determined from AFM images. The R_{RMS} varies between 3–5 nm for the thin film samples with the N₂ gas flow rate ranging from 0 to 15 sccm. Tauc plot analysis based on the optical transmittance spectra in the wavelength range from 400 to 1500 nm shows that the optical band gap energy is approximately 2.53 ± 0.02 eV, independent of the nitrogen concentration in the N-doped Cu₂O thin films, i.e., there is no apparent band-edge shift induced by the nitrogen doping. Room temperature Hall effect measurements show that the N:Cu₂O thin films display p-type conductivity and that the resistivity decreases with increasing N₂ gas flow rate. A resistivity of 1.9 Ω·cm was obtained for a N₂ gas flow rate of 15 sccm, compared to a resistivity of 190 Ω·cm the undoped Cu₂O reference sample. The majority carrier (hole) density for the N:Cu₂O thin films increases with the N₂ gas flow rate, e.g., a hole density of $\sim 3 \times 10^{19}$ cm⁻³ was obtained for a N₂ gas flow rate of 10 sccm, more than three order of magnitudes higher than the hole density recorded for the undoped Cu₂O reference sample. Furthermore, the hole mobility was found to decrease with increasing N₂ gas flow rate, i.e., for the undoped Cu₂O reference sample a hole mobility of 13 cm²/V·s was measured, whereas for the N-doped Cu₂O thin film sample processed with a N₂ gas flow rate of 15 sccm a hole mobility of 0.1 cm²/V·s was measured.

To conclude, we have shown that the electrical properties of Cu₂O thin films can be modified by nitrogen doping without considerably affecting the structural and optical properties. Potential applications for p-type N:Cu₂O films include all-oxide based p-n heterojunction devices, such as p-Cu₂O/n-ZnO photodetectors and solar cells. For example, the N:Cu₂O films can be incorporated at the back side of the Cu₂O absorber layer in a ZnO/Cu₂O heterojunction solar cell to reduce the charge carrier recombination at the rear surface and to form a low-resistivity ohmic contact at the rear interface.

Author Contributions: Conceptualization, Ø.N., R.K., K.B., S.E.F., E.M. and I.C.; Methodology, Ø.N., R.K.; Formal Analysis, Ø.N., R.K., K.B.; Investigation, Ø.N., R.K.; Funding Acquisition, Ø.N., E.M., S.E.F. and I.C.; Data Curation, Ø.N.; Writing-Original Draft Preparation, Ø.N.; Writing-Review & Editing, Ø.N.; Visualization, Ø.N.; Project Administration, Ø.N., E.M., I.C. and S.E.F.

Funding: The work was carried out in the research project “High-performance tandem heterojunction solar cells for specific applications (SOLHET)”, funded by the Research Council of Norway (RCN), project 251789, and the Romanian Executive Agency for Higher Education, Research, Development and Innovation Funding (UEFISCDI) through the M-Era.net program. RCN is also acknowledged for the support to the Norwegian Micro- and Nano-Fabrication Facility, NorFab, project number 245963/F50.

Acknowledgments: The authors would like to thank Mihaela Dinu and Adrian Kiss from the National Institute of Research and Development for Optoelectronics (INOE-2000) for assistance with the AFM measurements, and Alexander Azarov and Christoph Seiffert from the University of Oslo for carrying out the SIMS measurements.

Conflicts of Interest: The authors declare no conflict of interest.

References

- Shockley, W.; Queisser, H.J. Detailed Balance Limit of Efficiency of PN Junction Solar Cells. *J. Appl. Phys.* **1961**, *32*, 510–519. [[CrossRef](#)]
- Nordseth, Ø.; Kumar, R.; Bergum, K.; Fara, L.; Dumitru, C.; Crăciunescu, D.; Drăgan, F.; Chilibon, I.; Monakhov, E.; Foss, S.E.; et al. Metal Oxide Thin-Film Heterojunctions for Photovoltaic Applications. *Materials* **2018**, *11*, 2593. [[CrossRef](#)] [[PubMed](#)]
- Minami, T.; Nishi, Y.; Miyata, T. Cu₂O-based solar cells using oxide semiconductors. *J. Semicond.* **2016**, *37*, 014002. [[CrossRef](#)]
- Minami, T.; Nishi, Y.; Miyata, T. Efficiency enhancement using a Zn_{1-x}Ge_x-O thin film as an n-type window layer in Cu₂O-based heterojunction solar cells. *Appl. Phys. Express* **2016**, *9*, 052301. [[CrossRef](#)]
- Nordseth, Ø.; Kumar, R.; Bergum, K.; Fara, L.; Foss, S.E.; Haug, H.; Drăgan, F.; Crăciunescu, D.; Sterian, P.; Chilibon, I.; et al. Optical Analysis of a ZnO/Cu₂O Subcell in a Silicon-Based Tandem Heterojunction Solar Cell. *Green Sustain. Chem.* **2017**, *7*, 57–69. [[CrossRef](#)]
- Nordseth, Ø.; Haug, H.; Kumar, R.; Bergum, K.; Dragan, F.; Craciunescu, D.; Fara, L.; Chilibon, I.; Monakhov, E.; Foss, S.E.; et al. Performance optimization of a four-terminal Cu₂O/c-Si tandem heterojunction solar cell. In Proceedings of the 35th European Photovoltaic Solar Energy Conference and Exhibition, Brussels, Belgium, 24–28 September 2018.
- Siah, S.C.; Lee, Y.S.; Segal, Y.; Buonassisi, T. Low contact resistivity of metals on nitrogen-doped cuprous oxide (Cu₂O) thin-films. *J. Appl. Phys.* **2012**, *112*, 084508. [[CrossRef](#)]
- Zhang, X.; Wan, Y.; Bullock, J.; Allen, T.; Cuevas, A. Low resistance Ohmic contact to p-type crystalline silicon via nitrogen-doped copper oxide films. *Appl. Phys. Lett.* **2016**, *109*, 052102. [[CrossRef](#)]
- Kim, J.; Takiguchi, Y.; Miyajima, S. Characterization of p-type nitrogen-doped cuprous oxide/n-type hydrogenated microcrystalline silicon tunnel recombination junction for perovskite/crystalline silicon tandem solar cells. *Jpn. J. Appl. Phys.* **2018**, *57*, 08RB05. [[CrossRef](#)]
- Ishizuka, S.; Kato, S.; Maruyama, T.; Akimoto, K. Nitrogen Doping into Cu₂O Thin Films Deposited by Reactive Radio-Frequency Magnetron Sputtering. *Jpn. J. Appl. Phys.* **2001**, *40*, 2765–2768. [[CrossRef](#)]
- Sberna, P.M.; Crupi, I.; Moscatelli, F.; Privitera, V.; Simone, F.; Miritello, M. Sputtered cuprous oxide thin films and nitrogen doping by ion implantation. *Thin Solid Films* **2016**, *600*, 71–75. [[CrossRef](#)]
- Nakano, Y.; Saeki, S.; Morikawa, T. Optical bandgap widening of -type Cu₂O films by nitrogen doping. *Appl. Phys. Lett.* **2009**, *92*, 022111. [[CrossRef](#)]
- International Centre for Diffraction Data. Available online: <http://www.icdd.com/> (accessed on 12 June 2019).

14. Li, H.J.; Pu, C.Y.; Ma, C.Y.; Li, S.; Dong, W.J.; Bao, S.Y.; Zhang, Q.Y. Growth behavior and optical properties of N-doped Cu₂O films. *Thin Solid Films* **2011**, *520*, 212–216. [[CrossRef](#)]
15. Bennett, J.M.; Mattson, L. *Introduction to Surface Roughness and Scattering*; Optical Society of America: Washington, DC, USA, 1989.
16. Gan, J.; Venkatachalapathy, V.; Svensson, B.G.; Monakhov, E.V. Influence of Target Power on Properties of Cu_xO Thin Films Prepared by Reactive Radio Frequency Magnetron Sputtering. *Thin Solid Films* **2015**, *594*, 250–255. [[CrossRef](#)]
17. Malerba, C.; Ricardo, C.L.A.; D’Incau, M.; Biccari, F.; Scardi, P.; Mittiga, A. Nitrogen doped Cu₂O: A possible material for intermediate band solar cells? *Solar Energ. Mater. Solar Cell.* **2012**, *105*, 192–195. [[CrossRef](#)]



© 2019 by the authors. Licensee MDPI, Basel, Switzerland. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (<http://creativecommons.org/licenses/by/4.0/>).